


BRAZETEC BRAZING PASTE

## / BrazeTec Brazing Paste Systems


For innovative connection possibilities, BrazeTec also offers brazing materials as pastes, in addition to the solid forms. A brazing paste is a homogenous, ready to use, mixture of metallic brazing powder, flux and solvents. Polymers and other additives prevent the settlement of the brazing powder and determine the application and flow characteristics of the brazing paste. The following processes are available for the application according to the task in hand.

BrazeTec offers tailor-made brazing paste systems for these application processes. For this purpose, a wide range of binder systems and brazing paste formulations have been developed and can be further adapted for specific customer processes. Brazing pastes are particularly suitable for automated brazing processes, because they can be easily integrated into a production process. They enable the optimum use of materials for both small and large series production.


## / Application Processes

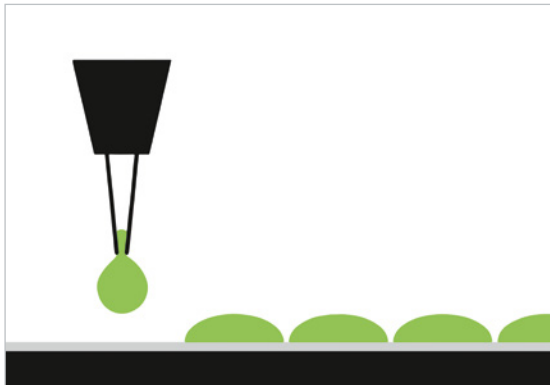


D = Dispensing

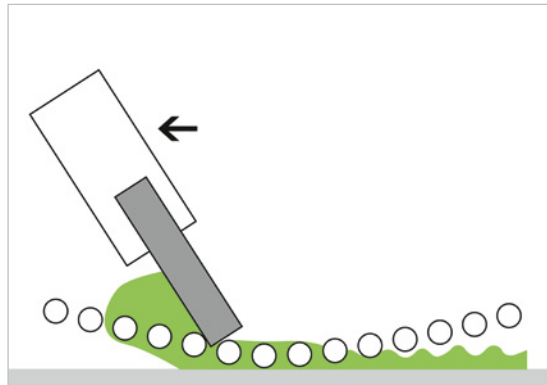

P = Screen-/Stencilprinting

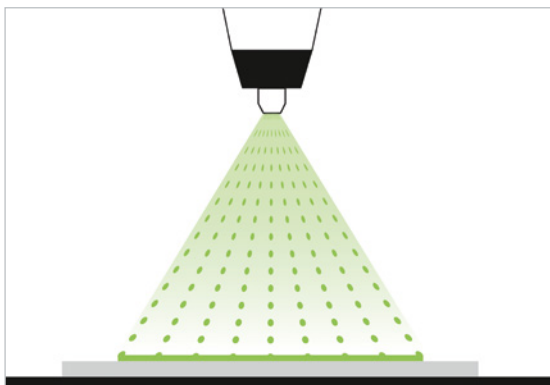

S = Spraying

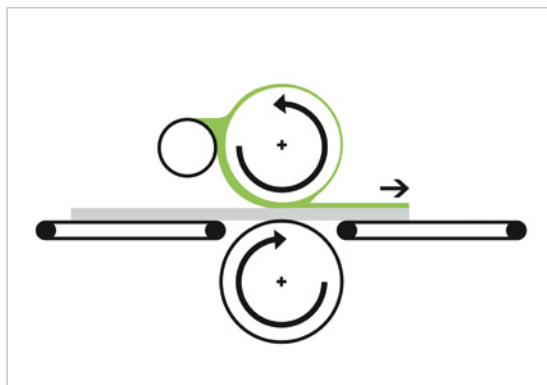

R = Rollercoating

## / BrazeTec Silver Based Brazing Paste

The silver based BrazeTec brazing pastes can be used to braze any steel, copper, nickel, and copper alloy. They can be applied with a dispenser or by screen printing. There is a risk of crevicecorrosion when brazing stainless steels if the braze contains zinc.

The brazing pastes shown below are available on a standard basis, and depending on the application, contain flux or are flux free. Additional alloys are available upon request.

Name	Composition by Weight-%						Melting Range acc. to DSC	Melting Range acc. to ISO 17672	Brazing Temp.	ISO 17672	Notes on Application
	Ag	Cu	Zn	Mn	Ni	Misc.	in °C	in °C	in °C		
BrazeTec D 7200	72	28	-	-	-	-	780	780	780	Ag 272	any steel, copper-Ni and Ni-alloys
BrazeTec D 5600	56	22	17	-	-	5 Sn	630 – 655	620 – 655	655	Ag 156	any steel, copper-Ni and Ni-alloys
BrazeTec D 4900	49	16	23	7.5	4.5	-	680 – 705	680 – 705	690	Ag 449	cemented carbides
BrazeTec D 4576	45	27	25,5	-	-	2.5 Sn	645 – 695	640 – 680	695	Ag 145	any steel, copper-Ni and Ni-alloys

## / BrazeTec Copper Based Brazing Paste

The CuproBraz®-Process was developed especially for the flux free brazing of copperbrass radiators in protective gas furnaces. The brazing material used in this process is a phosphorous containing copper alloy. The radiators are produced in a manner that displays high resistance with high working temperatures as well. In addition the entire CuproBraz®-Process is also notable for its low

costs. The different solvent based pastes can be applied by spraying onto the tubes (BrazeTec CST 600 TD) or through special roller-coating onto the fins. BrazeTec CSH 610 TD is used for the brazing of header plates to the tubes. These pastes can also be used for Cu-Cu-Brazing.

Name	Composition by Weight-%				Melting Range acc. to DSC		Melting Range acc. to ISO 17672	Brazing Temp.	ISO 17672	Atmosphere <sup>1)</sup>				Notes on Application
	Ag	Sn	Ni	P	Ag	in °C	in °C	in °C						
BrazeTec D 801	100	-	-	-	-	1,085	1,085	1,120	Cu 110	•	•	•	•	Any steel, Ni and Ni alloys
BrazeTec D 807	80	-	-	5	15	645 – 800	645 – 800	720	CuP 284	•	-	•	•	Cu and Cu alloys
BrazeTec D 810	92	-	-	8	-	710 – 770	710 – 770	750	CuP 182	•	•	•	-	Cu and Cu alloys

### Brazing paste systems for the CuproBraz® process

BrazeTec CST 600 TD	76	15.6	4.2	5,3	-	590 – 610	-	650	-	•	-	•	-	Paste for preliminary brazing of tubes by means of spray application for the CuproBraz® process
BrazeTec CSF 600 TD	76	15.6	4.2	5,3	-	590 – 610	-	650	-	•	-	•	-	Paste for preliminary brazing of fin tips by means of roller application for the CuproBraz® process
BrazeTec CSH 610 TD	78.5	9.3	5.7	6,5	-	595 – 620	-	650	-	•	-	•	-	Paste for preliminary brazing of connection plates in the CuproBraz® process, 2% flux proportion
BrazeTec CSO 610.2 TD	78.5	9.3	5.7	6,5	-	595 – 620	-	650	-	•	-	•	-	Paste for brazing of junction boxes by means of dispenser in the CuproBraz® process, 2% flux proportion

<sup>1)</sup> A = dry hydrogen B = vacuum C = H<sub>2</sub>N<sub>2</sub>-gas atmospheres (dew point -30 ° C) D = Exogas

## / BrazeTec Nickel Based Brazing Paste

Modern application-systems can be used for almost all known powder-type nickel-based brazing alloys. The products shown below are available as standard products from BrazeTec. Among

others, the application of the BrazeTec nickel-based brazing pastes is commonly practiced in heat exchangers and the automotive industry.

Name	Composition by Weight-%						Melting Range acc. to DSC		Melting Range acc. to ISO 17672	Brazing Temp.	ISO 17672	Atmosphere <sup>1)</sup>			Application Processes <sup>2)</sup>				
	Ni	Cr	Fe	Si	B	P	in °C	in °C	in °C			A	B	C	Solvent based Pastes			Water based Pastes	
															P	R	S	D	S
BrazeTec 897	76	14	-	-	-	10	890	890	980	Ni 710	•	•	•	•	-	•	-	•	•
BrazeTec 1002	82.4	7	3	4.5	3.1	-	970 – 1,000	970 – 1,000	1,050	Ni 620	•	•	-	•	•	•	•	•	•
BrazeTec 1090	60	30	-	4	-	6	980 – 1,040	-	1,090	-	•	•	•	-	•	-	-	•	•
BrazeTec 1130	72	18	-	8	-	2	1,050 – 1,090	-	1,080	-	•	•	•	-	-	-	-	•	-
BrazeTec 1135	70.9	19	-	10.1	-	-	1,080 – 1,135	1,080 – 1,135	1,190	Ni 650	•	•	•	•	•	•	•	•	•

<sup>1)</sup> A = dry hydrogen B = vacuum C = H<sub>2</sub>N<sub>2</sub>-gas atmospheres (dew point -30 ° C) <sup>2)</sup> D = Dispensing P = Screen-/Stencilprinting S = Spraying R = Rollercoating

**SAXONIA Technical Materials GmbH**

Rodenbacher Chaussee 4

63457 Hanau Germany

Tel. +49 6181 9061-0

Fax +49 6181 9061-4000

[technical.materials@saxonia-tm.de](mailto:technical.materials@saxonia-tm.de)

[www.saxonia-tm.de](http://www.saxonia-tm.de)